



Prüfbericht - Nr.: <i>Test Report No.:</i>	IND/BLR/CH/2021/2305R	Seite 1 von 3 <i>Page 1 of 3</i>			
ULR No.:	TC568821500002305F				
Auftraggeber: <i>Client:</i>	ENRICH ENCAP PRIVATE LIMITED SURVEY NO. 116/1/1/1, RUDANA VILLAGE, KHANVEL, 396230, INDIA				
Gegenstand der Prüfung: <i>Test item:</i>	ENCAP - S0398F				
Bezeichnung: <i>Identification:</i>	-	Serien-Nr.: <i>Serial No./ Document Submitted:</i>	Email Dated: 10.03.2021		
Wareneingangs-Nr.: <i>Receipt No.:</i>	12032021	Eingangsdatum: <i>Date of receipt:</i>	12.03.2021		
Order No.:	166535375	Testing Period:	17.03.2021 to 17.03.2021		
Prüfort: <i>Testing location:</i>	TÜV Rheinland India Pvt Ltd, Plot No. 27/B, 2nd Cross Road, Electronics City, Phase 1, Bangalore - 560 100, Karnataka, India.				
Prüfgrundlage: <i>Test specification:</i>	Customer's Requirement : Tensile Test				
Prüfergebnis: <i>Test Result:</i>	Refer Page No.: 2 to 3				
Prüflaboratorium/ Testing Laboratory:					
zusammengestellt/ compiled by:		kontrolliert/ checked by:			
 Raghukumar B S Sr. Engineer – Polymer Section, Material Testing Laboratories, Industry Services 31.03.2021		 Ranabir Pal Sr. Manager – Polymer Section, Material Testing Laboratories, Industry Services 31.03.2021			
Datum <i>Date</i>	Name <i>Name</i>	Unterschrift <i>Signature</i>	Datum <i>Date</i>	Name <i>Name</i>	Unterschrift <i>Signature</i>
Sonstiges/ Other Aspects: This is an amended test report and this report replaces the earlier report IND/BLR/CH/2021/2305 dated 18.03.2021. The report is amended to change the test item name as per client request.					
Abkürzungen:		Abbreviations:			
ok / P = entspricht Prüfgrundlage		ok / P = passed			
fail / F = entspricht nicht Prüfgrundlage		fail / F = failed			
n.a. / N = nicht anwendbar		n.a. / N = not applicable			
Dieser Prüfbericht bezieht sich nur auf das o.g. Prüfmuster und darf ohne Genehmigung der Prüfstelle nicht auszugsweise vervielfältigt werden. Dieser Bericht berechtigt nicht zur Verwendung eines Prüfzeichens.					
<i>This test report relates to the a. M. Test sample. Without permission of the test center this test report is not permitted to be duplicated in extracts. This test report does not entitle to carry any safety mark on this or similar products. Test item submitted by client. Sampling not done by TUVRI. Decision rule applied at 95% confidence level of measurement uncertainty with coverage factor k=2 while stating the conformity'</i>					

Prüfbericht - Nr.:
Test Report No.:

IND/BLR/CH/2021/2305R


Seite 2 von 3
Page 2 of 3

ULR No.:

TC568821500002305F

TEST RESULTS

Discipline: Mechanical
Product Group: Rubber and Rubber Products

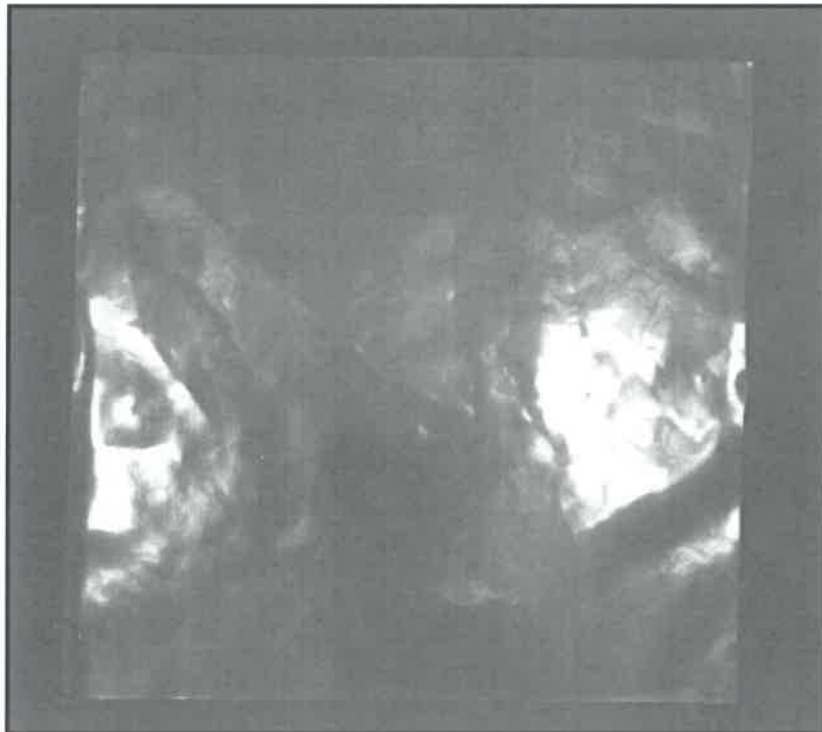

Photograph of sample as in received condition

Test Name: Tensile Test
Test Method: ASTM D412
Test Condition: Specimen type: Die C
Gauge length: 25 mm
Test speed: 500 mm/min

Observation:

Direction A

Specimen No.	Tensile Strength (MPa)	Elongation @ Break (%)
1	19.5	596
2	19.9	605
3	17.9	598
Average	19.1	600





TC- 5688



Prüfbericht - Nr.:
Test Report No.:

IND/BLR/CH/2021/2305R

Seite 3 von 3
Page 3 of 3


ULR No.:

TC568821500002305F


Direction B

Specimen No.	Tensile Strength (MPa)	Elongation @ Break (%)
1	18.4	609
2	20.0	624
3	21.8	611
Average	20.1	615

Direction A

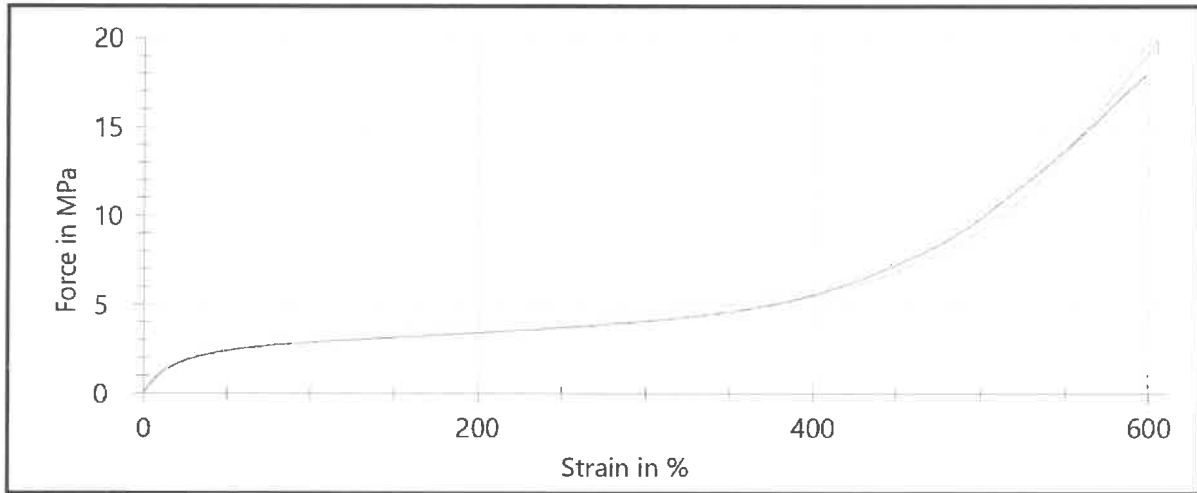

Direction B

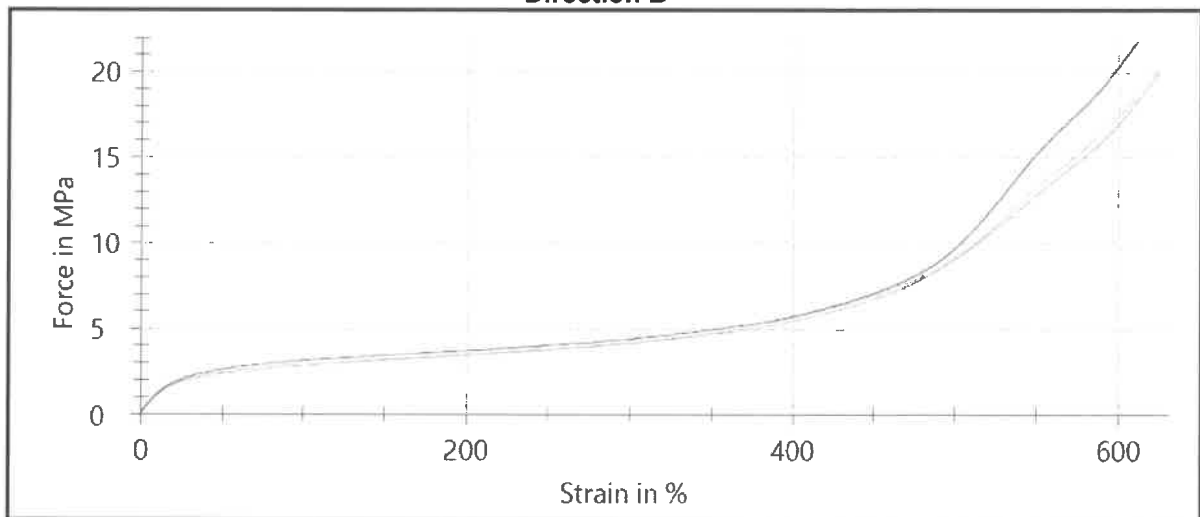

Test Graphs

---- End of Report ----